

## Influence of Dopants on Mechanical Properties of Steel: A Spin-Polarized Pseudopotential Study

 Zavodinsky V<sup>1\*</sup> and Kabaldin Y<sup>2</sup>
<sup>1</sup>Institute for Materials Science of the Russian Academy of Sciences 153 Tikhoookeanskaya str., Khabarovsk, 680042, Russia

<sup>2</sup>Nizhny Novgorod State Technical University, 24 Minin str. Nizhny Novgorod, 603013, Russia

### Abstract

Density functional theory and pseudopotentials were used to study reaction of the ferrite grains interface (doped with C, P, N, Ti, Ti+N and Ti+C) on deformations. It was shown that impurities could increase or decrease the tensile strength and the elongation limit. The best effect was demonstrated for cases when Ti presents simultaneous with C; the worst case is doping iron with P. As for the shift modulus, effect is not significant.

**Keywords:** Ab initio simulation;  $\alpha$ -Fe; Tensile strength; Shift modulus; Dopants influence

### Introduction

Low carbonized steel is a well-known Fe alloy used as a material for various engineering details and constructions. Usually it contains up to 0.2 per cent of carbon and some small amounts of other dopants. There are some works where influence of dopants on the mechanical properties of steel is studied on the atomic level [1-5]. However, in the most of them only some energetic characteristics are studied, while engineers are interested in technical parameters. Here we present results of the tensile strength and the shift modulus calculations for the doped Fe.

### Methods and Models

As real steel is a polycrystalline material consisted mainly of  $\alpha$ -Fe grains, its durability depends mainly on the durability of grain interfaces (borders). For this reason our investigation is limited with studying of the interface between two grains of  $\alpha$ -Fe.

It is well known that  $\alpha$ -Fe is a ferromagnetic with magnetic polarization of  $2.2 \mu_B$  per atom, bcc-lattice with period  $a=2.867 \text{ \AA}$ , and cohesion energy of 5.48 eV. In this work we used the spin-polarized version of DFT realized within the FHI96md package [6] based on the density functional theory (DFT) [7,8] and the pseudo-potential method [9]. This package was previously used with advantage for many systems, including transition metal compositions [10-14]. In all cases, the generalized gradient approximation [15] to description of the exchange-correlation interactions has been chosen and the optimization of the atomic geometry has been performed. All pseudopotentials were constructed with the FHI98PP package [16]. They were checked for the absence of the so-called 'ghost' states and were used for founding the equilibrium lattice parameters, magnetic and the cohesion energy of  $\alpha$ -Fe.

To model the bulk bcc  $\alpha$ -Fe we used a cubic cell with two iron atoms: one atom was placed in the lattice cell corner; the second atom was situated in the center of the cell. The energy cut-off for the plane wave set was equal to 40 Ry and the special k-point (0.25; 0.25; 0.25) was used. The self-consistency convergence was provided by stabilizing the total energy with an accuracy of 0.005 eV per atom. We have found the equilibrium lattice constant of 2.88  $\text{\AA}$ , magnetic moment of 2.0  $\mu_B$ , and cohesion energy of 4.5 eV, in satisfactory accordance with experimental data.


An interface between two  $\alpha$ -Fe grains was modeled as a contact

of two thin crystalline slabs having infinity dimensions in X and Y directions. Thickness of the each slab was made of three atomic layers. The interacting slabs approached among themselves before the minimum of their total energy was achieved. The scheme of such system is given in Figure 1.

In order to test our approach we calculated the interface energy (the energy gain of iron grains bonding) and have obtained the value of 1.33 J/m<sup>2</sup>. According to refs. [5,17] published values of the grain interface energy of Fe lie in the interval of 0.47-1.63 J/m<sup>2</sup>.

After leading of the system in a state with the minimum energy we made computer experiments of two types (Figure 2). The top panel: investigation of the reaction of the interface to break; the down panel: investigation of the reaction of the interface to shift.

In the stretch case we found the variations of the total energy  $\Delta E$  as functions of elongation  $\Delta Z$ , and then the applied strength P was

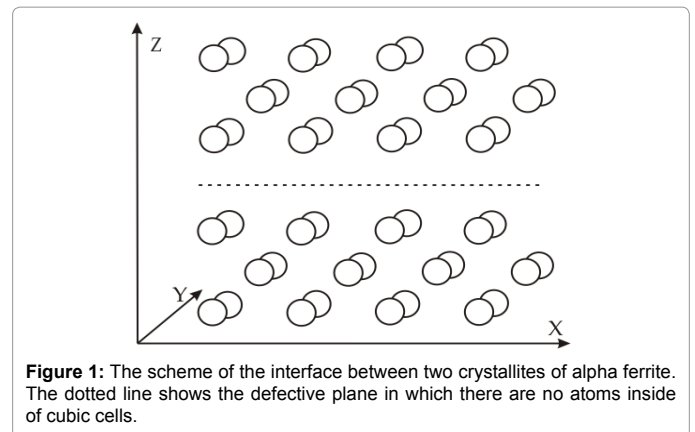

**\*Corresponding author:** Victor Zavodinsky, Institute for Materials Science of the Russian Academy of Sciences 153 Tikhoookeanskaya str., Khabarovsk, 680042, Russia, Tel: 07(4212)226956; Fax: 07(4212)226598; E-mail: [vzavod@mail.ru](mailto:vzavod@mail.ru)

Received June 24, 2017; Accepted July 11, 2017; Published July 21, 2017

**Citation:** Zavodinsky V, Kabaldin Y (2017) Influence of Dopants on Mechanical Properties of Steel: A Spin-Polarized Pseudopotential Study. J Material Sci Eng 6: 354. doi: 10.4172/2169-0022.1000354

**Copyright:** © 2017 Zavodinsky V, et al. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.



calculated according the formulae  $P = \frac{\Delta E}{\Delta Z} \frac{1}{S_{XY}}$ , where  $S_{XY}$  is the system square in the XY plane. In the shift case we studied the dependence of  $\Delta E$  on  $\text{tg}\phi$ , where  $\phi$  is the shift angle, and calculated the shift module  $G = \frac{\Delta E}{\Delta X} \frac{1}{S_{XY}} \frac{1}{\text{tg}\phi}$ .

## Results and Discussion

### Undoped $\alpha$ -Fe

First of all we studied reaction of the undoped iron system on stretching along Z direction and on shift along X direction. Atoms of upper and down planes were moved step-by-step and fixed at the each step. Other atoms were able to relax up and to find equilibrium positions. The dependences of tension on elongation and energy on tangent of the shift angle are presented in Figure 3.

The top panel of this figure demonstrates the strength limit of 18 GPa for breaking the undoped  $\alpha$ -Fe grains interface. The down panel shows that the shift process has two stages. Firstly, the total energy grows sharply with the shift modulus of 160 GPa; secondly, the shift modulus decreased to 80 GPa. Comparatively, experimental value of

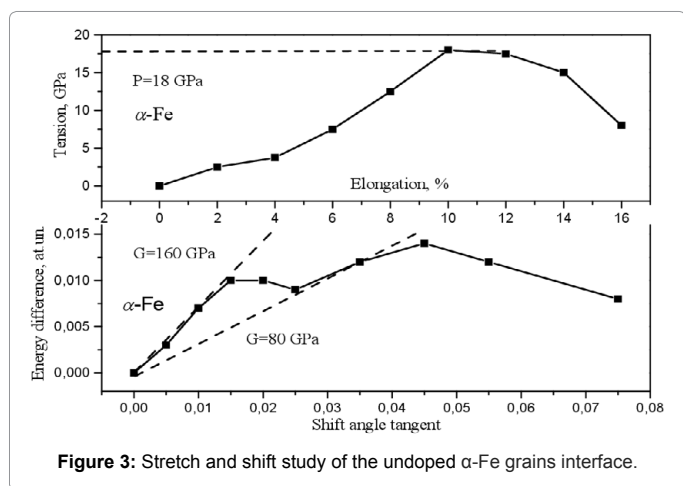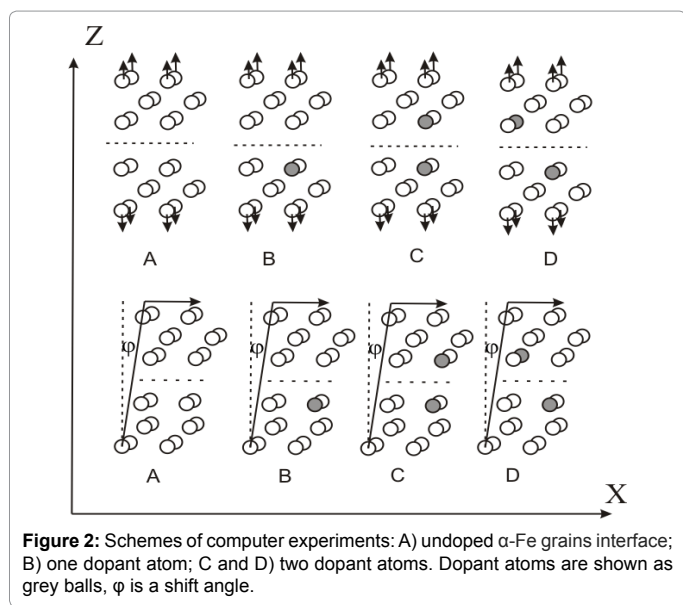

tensile strength is 60 MPa for the low carbonized steel and 1.3 GPa for single-crystalline whiskers. The published shift module value is 14 GPa [3].

### Dopants influence


We placed dopant atoms as it is shown in Figure 2B-2D. Namely, for single-atomic cases we replaced one atom of the interface with C, P, N or Ti atom. For two-atomic cases (TiN or TiC) dopant atoms were placed on both sides of the interface. Results of calculations are presented in Figure 4 and Table 1.

It is clear (Figure 4) that presence of carbon increases the tensile strength by 1.5 times in comparison with undoped ferrite; N and Ti+N decrease it approximately by 20 percent. The Ti and Ti+C cases demonstrate the tensile strength very close to the case of undoped iron. At another hand addition of carbon reduces the limit of elongation to 1 percent (for undoped  $\alpha$ -Fe it is 10 percent); nitrogen reduces it to 8 percent; while Ti, Ti+N and Ti+C increase its value up to 14-18 percent. As for phosphorus it decreases strongly both the tensile strength and the limit of elongation. In more details results are collected in Table 1.

Influence of dopants on the shift behavior of the Fe grains interface is much less significant than their effect for the stretch characteristics. Our modeling shows that in all doped cases the dependence of the shift module on the shift angle tangent looks like that of the undoped Fe case, and its value varies between 70 and 170 GPa.

### Conclusion

Quantum-mechanics modeling of the  $\alpha$ -Fe grains interface as a contact of two nano thin slabs lets us to obtain adequate data of dopants influence (C, P, N, Ti, Ti+C and Ti+N) on mechanical properties of steel. Summarize all results we can conclude that addition of Ti (single or with C) increases significantly the elongation limit keeping approximately the level of the tensile strength of un-doped iron. Thus, addition of Ti in the C doped  $\alpha$ -Fe can improve elasticity of steel details and constructions at low temperatures. Phosphorus is the worst impurity in steel.

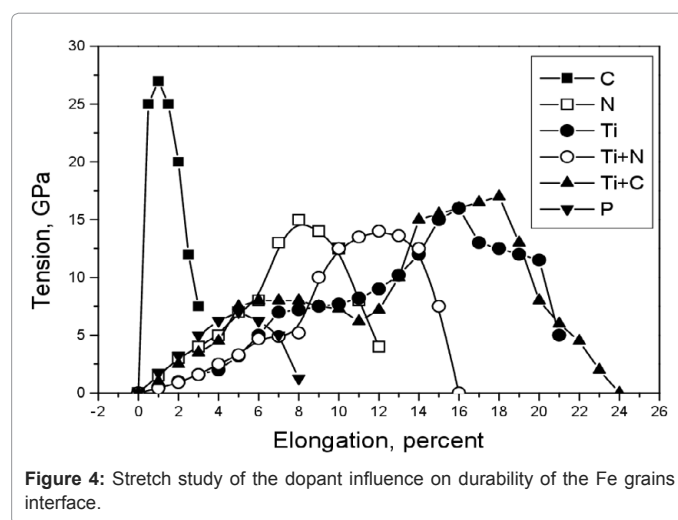

System	Undoped Fe	Fe+C	Fe+N	Fe+Ti	Fe+Ti+C	Fe+Ti+N	Fe+P
P, GPa	18	27	14.8	15.5	16.5	14.5	7.1
L, percent	10	1	8	16	18	12	5

Table 1: Tensile strength  $P$  and elongation limit  $L$  for the Fe grains interface.

## References

1. Kolesnikov V, Myasnikova N, Sidashov A, Myasnikov P, Kravchenko J, et al. (2010) Multilayered antifriction nanostructure covering for lubrication in the tribocoupling "wheel-rail". *Transport problems* 5: 71-79.
2. Ridny YaM, Mirzoev AA, Mirzaev DA (2014) Ab initio modelirovanie azota v GTsK-reshotke zheleza. *Vestnik Yuzhnogo Gosudarstvennogo Universiteta. Ser. Metallurgiya (in Russian)* 14: 59-63.
3. Hu SY, Ludwig M, Kizler P, Schmauder S (1998) Atomistic simulations of deformation and fracture of. *Modelling and Simulation in Materials Science and Engineering* 6: 567.
4. Oila A, Bull SJ (2009) Atomistic simulation of Fe-C austenite. *Computational Materials Science* 45: 235-239.
5. Verkhoviykh AV, Mirzoev AA (2013) Ab initio modelirovanie energii formirovaniya granitsy zerna v OTsK-zheleze. *Vestnik Yuzhno-Uralskogo Gosudarstvennogo Universiteta. Ser. Metallurgiya, Mekhanika, Fizika (in Russian)* 5: 76-81.
6. Bockstedte M, Kley A, Neugebauer J, Scheffler M (1997) Density-functional theory calculations for poly-atomic systems: electronic structure, static and elastic properties and ab initio molecular dynamics. *Computer physics communications* 107: 187-222.
7. Hohenberg P, Kohn W (1964) Inhomogeneous electron gas. *Physical Review* 136: B864.
8. Kohn W, Sham LJ (1965) Self-consistent equations including exchange and correlation effects. *Physical review* 140: A1133.
9. Heine V, Weaire D (1970) Pseudopotential theory of cohesion and structure. *Solid State Physics* 24: 249-463.
10. Dabrowski J, Müssig HJ, Zavodinsky V, Baierle R, Caldas MJ (2002) Mechanism of dopant segregation to SiO<sub>2</sub>/Si (001) interfaces. *Physical Review B* 65: 245305.
11. Zavodinsky VG (2004) The mechanism of ionic conductivity in stabilized cubic zirconia. *Physics of the Solid State* 46: 453-457.
12. Zavodinsky VG, Chibisov AN (2006) Zirconia nanoparticles and nanostructured systems. *Journal of Physics: Conference Series* 29: 173. IOP Publishing.
13. Zavodinsky VG (2010) Small tungsten carbide nanoparticles: Simulation of structure, energetics, and tensile strength. *International Journal of Refractory Metals and Hard Materials* 28: 446-450.
14. Zavodinsky VG (2011) Cobalt layers crystallized on the WC (100) surface: Spin-polarized ab initio study. *International Journal of Refractory Metals and Hard Materials* 29: 184-187.
15. Perdew JP, Burke K, Wang Y (1996) Generalized gradient approximation for the exchange-correlation hole of a many-electron system. *Physical Review B* 54: 16533.
16. Fuchs M, Scheffler M (1999) Ab initio pseudopotentials for electronic structure calculations of poly-atomic systems using density-functional theory. *Computer Physics Communications* 119: 67-98.
17. Chicago Zybin IN, Bulychev VV, Latypov RA (2015) Analiz energii granits zeren v metallakh primenitelno k protsesu soedinenia metallov pri svarke davleniem. *Sovremennye Problemy Nauki i Obrazovania* 1: 18-23.

**Citation:** Zavodinsky V, Kabaldin Y (2017) Influence of Dopants on Mechanical Properties of Steel: A Spin-Polarized Pseudopotential Study. J Material Sci Eng 6: 354. doi: [10.4172/2169-0022.1000354](https://doi.org/10.4172/2169-0022.1000354)

## OMICS International: Open Access Publication Benefits & Features

### Unique features:

- Increased global visibility of articles through worldwide distribution and indexing
- Showcasing recent research output in a timely and updated manner
- Special issues on the current trends of scientific research

### Special features:

- 700+ Open Access Journals
- 50,000+ Editorial team
- Rapid review process
- Quality and quick editorial, review and publication processing
- Indexing at major indexing services
- Sharing Option: Social Networking Enabled
- Authors, Reviewers and Editors rewarded with online Scientific Credits
- Better discount for your subsequent articles

Submit your manuscript at: <http://www.omicsgroup.org/journals/submission>